

Controlling of *Pseudomonas syringae* by Nanoparticles Produced by *Streptomyces bikiniensis*

Ahmed Abdel-Megeed^{1,2}

¹Faculty of Agriculture (Saba Basha), Department of Plant Protection, Alexandria University, 22 Tag El Roassa Street. Bolky, 21531, Egypt.

²Department of Botany and Microbiology, College of Science, King Saud University, P.O. Box: 2455 Riyadh 11451, Saudi Arabia.

(Received: 09 March 2013; accepted: 22 April 2013)

Innovative approaches will be required to improve the methods for controlling and destruction of certain plant pathogens. Synthesis of nanoparticles with interesting physico-chemical properties using efficient as well as eco-friendly technology is one of the main objectives of nanotechnology. In the current study, *Streptomyces bikiniensis* was isolated from soil, Riyadh, Saudi Arabia, and identified by 16S rRNA. This study showed that the shape of silver nanoparticles (AgNPs) was predominantly monodispersed and spherical shapes in the size range of 5–35 nm upon addition of 1 mM silver nitrate. The AgNPs were characterized by determining Fourier transform infrared spectroscopy (FTIR), Energy Dispersive Spectroscopy (EDS) and transmission electron microscopy (TEM). Furthermore, the biosynthesized AgNPs at 5 μ l significantly inhibited the growth of one of the important Gram-negative bacterium *Pseudomonas syringae*. Thus, bioconversion of silver nanoparticles by *Streptomyces bikiniensis* could be employed as a potential nanoparticle biopesticides to control the plant pathogen, *Pseudomonas syringae*.

Key words: Plant pathogen, *Pseudomonas syringae*, AgNPs, *Streptomyces bikiniensis*, SEM.

Plant diseases cause severe crop losses and make agriculture highly dependent on adequate disease control. Managing and controlling plant diseases efficiently is important for crop growers, environmentalists, legislators, policy maker and implementers (Kumar *et al.*, 2007). Plant disease management strategies primarily depend on sanitary practices and well-timed pesticides applications. Many plant diseases heavily depend on agrochemicals and mainly rely on pesticides (Klaus *et al.*, 2001). These pesticides can prevent infection but not all have curative activity; therefore the interval between sprayings is usually short.

Pseudomonas syringae is a plant pathogen which can infect a wide range of plant species, and exists as over 50 different pathovars (Fei, 2011). This Gram negative bacterium is responsible for diseases in cultivated tomato, potato, cherry, plum, peach and apricot as well as in wild cherry, and has been still of concern with economic importance in these crops worldwide (Kaluzna *et al.*, 2010). This plant pathogen has attacked them under greenhouse and field conditions. Subsequently, plant pathogens are responsible for large amounts of chemical pesticides applied annually exacerbating control strategies (Niederhauser, 1993).

P. syringae is a member of the *Pseudomonas* genus, and based on 16S rRNA analysis, it has been placed in the *P. syringae* group (Anzai *et al.*, 2000). Many but not all strains secrete the lipodepsinonapeptide toxin syringomycin

* To whom all correspondence should be addressed.
Tel.: +966-1-4676940; Fax: +966-1-4675833;
E-mail: hekemdar@yahoo.com

(Scholz-Schroeder *et al.*, 2003) and it owes its yellow fluorescent appearance when cultured in vitro on King's B medium to production of the siderophore pyoverdinin (Cody and Gross, 1987). Owing to early availability of the genome sequence for three *P. syringae* strains and the ability of selected strains to cause disease on well-characterized host plants including *Arabidopsis thaliana*, *Nicotiana benthamiana*, and tomato.

To cope with these problems and due to the increase of public concern about adverse effects of agrochemicals on food safety and environment, there is need to stimulate the search for control strategies that are more durable and preferably based on natural products. Therefore, alternative approaches that can be incorporated into integrated pest management of plant diseases are needed.

The economic importance of the plant diseases and lack of effective control measures stimulated recent studies for controlling this pathogen. New technique of controlling is based on nanotechnology (Bhattacharya and Gupta, 2005). Nanoparticles are at the important advantage of the quickly emergent field of nanotechnology and they are currently made by chemical and physical approaches (Cody and Gross, 1987). The development of environmentally friendly, kindly and green process technologies for the production of nanoparticles with a range of chemical and physical properties is one of the challenges in the newly emerging field of nanobiotechnology (Dura *et al.*, 2005). The expensive and extensive use of toxic solvents and hazardous reducing agents in chemical procedures to synthesize nanoparticles has augmented the necessity in view of eco-friendly and green chemistry approach (Fei, 2011). Hence, a well-established non-toxic and eco-friendly potent methodology for the synthesis of nanoparticles has mounted to a level of supreme importance (Mukherjee *et al.*, 2008).

Over the last few years, the biosynthesis of nanoparticles by bacteria, fungi, and plant has gained much of interest of good conductivity, chemical, stability, catalytic and antimicrobial activity (Sivalingama *et al.*, 2012; Antony *et al.*, 2011). Sadhasivam *et al.*, (2010) used the extracellular components from a *Streptomyces hygrosopicus* culture medium to synthesize silver nanoparticles, and characterized their antimicrobial

activity (Mohanpuria *et al.*, 2008). *Streptomyces* sp. is members of gram positive, soil inhabiting filamentous actinomycetes characterized based on its complex life cycle. The genus is well known for its unique potential ability to produce a wide variety of secondary metabolites, such as antibiotics, immunosuppresses and many other biologically active compounds (Sadhasivam *et al.*, (2010). Exploitation of *Streptomyces* in nanotechnology has recently received considerable attention (Chater, 1993).

The present study aims at controlling of *Pseudomonas syringae* to maintain the quality and abundance of food, feed, and fiber produced by growers around the world. For achieving this goal biosynthesize silver nanoparticle by *Streptomyces bikiniensis* was isolated and their potential role for controlling *Pseudomonas syringae* was evaluated.

MATERIALS AND METHODS

Collection of soil samples and isolation of *Streptomyces bikiniensis*

Soil sample was collected in sterile airlock polythene bags and stored at 4°C from Al-Kharj area, Riyadh, Saudi Arabia. Soil sample was inoculated on starch casein agar medium (Pisano *et al.*, 1986) supplemented with antibiotics such as cycloheximide (40 g/l), nystatin (30 g/l) and nalidixic acid (10 g/l). The plates were incubated at 30 °C until the appearance of colonies with a tough leathery texture, dry or folded appearance, and branching filaments with aerial mycelia (Mince *et al.*, 2002). Pure colonies were isolated and subcultures were carried out by streaking the particular isolate directly on yeast extract-malt extract agar (ISP-2 medium (Hayakawa and Ohara, 1987).

Characterization of *Streptomyces bikiniensis* and culture conditions

Total genomic DNA of actinomycete isolate was extracted by a modification of a method of Smoker and Barnum (Smoker and Barnum, 1988). Actinomycete isolate was grown in 10 ml International Streptomyces Project Medium 2 (ISP 2) (Shirling and Gottlieb, 1966) with agitation at 30 °C for 96 h. Cells (4 ml) were harvested by centrifugation (12000 rpm for 2 min), washed once with 500 ml of 50mM Tris-HCl/1 mM EDTA (TE)

buffer (pH 8.0), the pellet was suspended in 500 ml of 50 mM Tris-HCl (pH 8.0)–5 mM EDTA (pH 8.0)–50 mM NaCl, add 20 µl lysozyme (1 mg/ml), and the solution was incubated at 55°C for 30 min. After the addition of 10 µl of proteinase K (10 mg/ml) and 20 µl of 10% sodium dodecyl sulfate, the mixture is incubated at 55°C for 10 min or until the solution cleared (complete cell lysis). The solution was chilled on ice and extracted with an equal volume of phenol-chloroform-isoamylalcohol (25:24:1).

The organic extraction was repeated. The supernatant was added to an equal volume of 4 M ammonium acetate. Total genomic DNA was precipitated by the addition of 2 volumes of isopropanol followed by centrifugation (13000 rpm) for 10 min at room temperature. Supernatant was removed after centrifugation (13000 rpm) and pellet was washed with 70% ethanol. The pellet was dissolved in 100 µl of TE buffer or double distilled water. The 16S ribosomal DNA gene was amplified by PCR using the universal primer pair 27F^{5'}-AGAGTTTGATCMTGGCTCAG^{3'} and 1492R^{5'}-ACCTTGTTACGACTT^{3'}. The amplified products were analyzed by Macrogen Inc., South Korea. DNA sequence analysis was then performed by BLAST network services at the NCBI. The 16S rRNA gene sequence of the isolate was aligned with reference sequences obtained from GenBank using Clustal (Thompson *et al.*, 1997). Phylogenetic tree was generated using the neighbor-joining method with MEGA 5 package (Saitou *et al.*, 1987; Kumar, Yadav, 2009). The evolutionary distance matrix was derived with Jukes and Cantor model (Jukes, and Cantor, 1969). Topology of phylogenetic tree was evaluated by bootstrap analysis based on 1000 replicates (Felsenstein, 1985).

Biosynthesis and characterization of AgNPs

The isolate was further cultured in ISP2 medium (pH 7.2) and grown for 72 h at 30 °C in an orbital shaker at 220 rpm. Cell filtrate (CF) was obtained by centrifugation at 4 °C, 10,000 rpm for 10 min. Bioreduction process to occur, AgNO₃ (Qualigens 99.8%) was added to 100 ml CF at molarity 1 mM and incubated at 30 °C in dark for 48 h. Followed by initial observation of color change in the bioreduction process, UV–visible spectrometric measurements were performed on Hitachi double beam equipment (Model Lambda

35) at range 210 to 800 nm. The bio-transformed products present in cell-free filtrate after 72 h of incubation were freeze-dried and diluted with potassium bromide in the ratio of 1: 100. FTIR spectrum of samples was recorded on FTIR instrument mode Nicolet 6700 spectrometer at a resolution of 4 cm⁻¹ in the range of 400–4000 cm⁻¹.

For energy dispersive spectroscopy (EDS), sample was prepared on a copper substrate by drop coating of silver nanoparticles, and was carried out using JEOL (JSM-6380 LA) equipped with scanning electron microscopy. Transmission electron microscopy was performed on JEOL (JEM-1010) instrument, with an accelerating voltage of 80 kV after drying of a drop of aqueous AgNPs on the carbon-coated copper TEM grids. Samples were dried and kept under vacuum in desiccators before loading them onto a specimen holder. The particle size distribution of silver nanoparticles was evaluated using Image J 1.45s software.

Efficacy of biosynthesized AgNPs against *Pseudomonas syringae*

The antibacterial activity of biosynthesized AgNPs was assessed against the pure bacterial strain of *Pseudomonas syringae* ATCC11528. The pathogen was provided from Research central laboratory, King Saud University, Riyadh. *Pseudomonas syringae* was maintained at 4°C for further experiment. The bacterial strain was grown again in liquid nutrient medium (M1) separately and overnight cultures were kept for 24 h at 37°C ± 1°C and the purity of cultures was checked after 8 h of incubation.

The antimicrobial effects of the microbiologically synthesized AgNPs were evaluated using method of disk inhibition zone. In disk inhibition zone method, the nutrient agar medium was inoculated with freshly prepared cells of *Pseudomonas syringae* on agar nutrient medium. After solidification of the agar, a number of sterilized disks were dipped into CF as positive control and biosynthesized AgNPs, and placed on the plates. After incubation at 37°C for 24 h, the antimicrobial activity was measured as diameter of the inhibition zone formed around the disk.

Scanning Electron Microscopy

The inhibited bacteria by biosynthesized silver nanoparticles were prepared for scanning electron microscope (SEM). The paper disc containing bacteria were fixed in 3 % (v/v)

glutaraldehyde buffered with 0.1 M sodium phosphate buffer (pH 7.2) for an hour at room temperature and then washed four times in sodium phosphate buffer. It was then post-fixed in 1 % (w/v) osmium tetroxide (OsO₄) for an hour and then washed four times in the buffer. They were dehydrated in a graded alcohol series. The last stages of dehydration were performed with propylene oxide. The specimens were dried and were mounted onto stubs using double-sided carbon tape, and then were coated with a thin layer of gold by a Polaron SC 502 sputter coater, and were examined in a Jeol JSM 6060 LV scanning electron microscope (Hayat, 1981).

RESULTS AND DISCUSSION

The total length of the 16 S rRNA gene sequenced in the present study possess 1446 base pair, and showed 100% similarity index with *S. bikiniensis* strain xsd08097 (GeneBank, Accession No. J481054.1). The result of cladistics analysis of generated sequence together with the related sequences accession retained from geneBank was consistent with the result of Blast search (Fig. 2); and here, the isolate was named as *S. bikiniensis* strain xsd08097 isolate (Fig. 1).

Fig. 3 shows the change in color of a mixture of the cell filtrate after mixing with silver



Fig. 1. (a) *S. bikiniensis* on SPI-2 medium, (b) Under light microscope 100x under microscope at 100X



Fig. 2. The phylogenetic tree of *S. bikiniensis* was constructed using the neighbor-joining method with aid of MEGA 5.0 program. The Bootstrap values above 50%, presented as percentages of 500 replications, are shown at the branch points. Bar 0.5 substitutions per nucleotide position

nitrate solution occurred, and this indicates the synthesis of silver nanoparticles by *S. bikiniensis*. Mulvaney (Mulvaney, 1996) also reported that the dark brown color is the result of excitation of surface plasmon vibration in the metal nanoparticles and is typical of the silver nanoparticles. It was observed that the color development was result as different reductase enzymes in filtrate of *streptomyces* sp. The role of NADH dependent nitrate reductase from fungi in the biosynthesis of silver nanoparticles was recently reported (Bai *et al.*, 2011); however, different NADH-dependent reductases may be produced also by *S. bikiniensis*. There was previously study used a *streptomyces* filtrate to produce Ag nanoparticles (Sadhasivam *et al.*, 2010).

Results of energy dispersive spectroscopy (EDS) of the silver nanoparticles was confirmed the presence of elemental silver signal shown in Fig. 4. The presence of an optical absorption band at ~3ev reveals the presence of pure metallic silver nanoparticles. Magudapathy *et al.*, (2001) also reported that the spectrum of nanoparticles sample showed mainly Ag (94.1%) and only minor amounts of other elements (5.9%), the signals for N and O indicate the presence of proteins as a capping material on the surface of silver nanoparticles.

The FTIR spectroscopy is very important to characterize the protein binding with the silver nanoparticles and it is possible to quantify secondary structure in metal nanoparticle-protein interaction. Fig. 5 shows FTIR spectrum of the present study which revealed two bands at 1634.92 cm^{-1} that corresponds to the bending vibrations of the amide I and amide II bands of the proteins while their corresponding stretching vibrations of primary amines were seen at 3453.17 cm^{-1} . Similarity, Gole *et al.*, (2001); Jain *et al.*, 2011) also reported the presence and binding of protein with silver nanoparticles which can lead to their possible stabilization.

Results in Fig.6 showed different sizes of nanoparticles, mostly spherical in shape but aggregated to a lesser extent. In Fig.7, there were four distinct sizes of Ag nanoparticles produced by *S. bikiniensis*. The size of Ag nanoparticles was approximately 4.2 nm with standard deviation 2.3nm, 33.3% was at 1 nm, 25.1% at 3 nm, 8.3% at 5 nm and 33.3 % at 7 nm. Sadhasivam *et al.*, (2010)

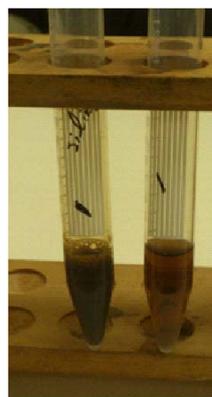


Fig. 3. Test tubes containing the filtrate of the *S. bikiniensis* at before addition 1 mM AgNO₃ (right) and after 72 h incubation with 1 mM AgNO₃ (left)

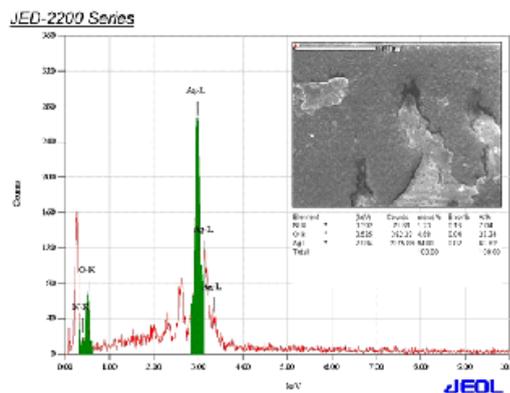


Fig. 4. EDS spectra of silver nanoparticles

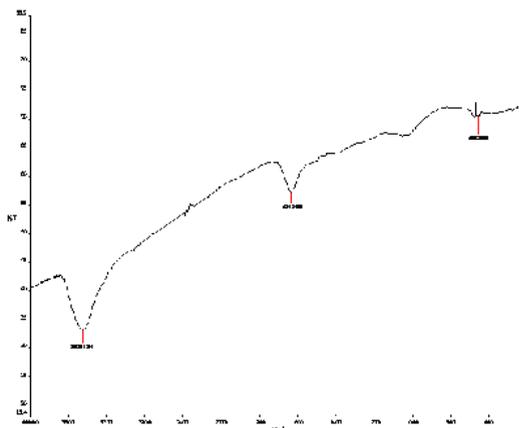


Fig. 5. FTIR spectrum of AgNPs synthesized by using cell free supernatant of *S. bikiniensis*

reported nanoparticle sizes of 20–30 nm when produced by the extracellular from a *Streptomyces* culture. This result was similar to previous study (Saifuddin *et al.*, 2009) for biosynthesis of silver nanoparticles from *Bacillus subtilis* using microwave radiation. The different size distribution of nanoparticles may be due to differences in reductases produced by *S. bikiniensis*, or the effects of other proteins coating the nanoparticles. The size distribution of nanoparticles can be very important for application purposes. For example, smaller nanoparticles were more effective as an antimicrobial against pathogens (Elechiguerra *et al.*, 2005).

Fig. 8 clearly showed the biosynthesized nanoparticles induced the formation of inhibition zone of test pathogen. Shrinking of the cell and degradation of cell was observed under SEM (Fig. 9). Stoimenov *et al.*, (2002), also confirmed that reactive metal oxide nanoparticles possess excellent bactericidal effects. The mechanism of inhibitory action of silver ions on microorganisms revealed that upon Ag^+ treatment, DNA loses its replication ability (Feng *et al.*, 2000) and expression of ribosomal subunit proteins as well as some other cellular proteins and enzymes essential to ATP production becomes inactivated (Yamanaka *et al.*, 2005). It had also been hypothesized that Ag^+ primarily affects the function of membrane-bound enzymes, such as those in the respiratory chain (Bragg *et al.*, 1974; McDonnell and Russell, 1999).

However, the mechanism of bactericidal actions of silver nanoparticles is still not well understood. In a previous report (Sondi and Salopek-Sondi, 2004) on the bactericidal activity of silver nanoparticles, it was shown that the interaction between silver nanoparticles and constituents of the bacterial membrane caused structural changes in or damage to membranes, finally leading to cell death.

In fact, for the past few decades, there has been a considerable in research interest in the area of natural product delivery using particulate for controlling plant pathology. The secondary metabolites in plants have been used in the formulation of nanoparticles through increase the effectiveness of therapeutic compounds used to reduce the spread of plant diseases, while minimizing side effects for being: rich source of

bioactive chemicals, biodegradable in nature and non-polluting (eco-friendly). Particulate systems like Nanoparticles have been used a physical approach to alter and improve the effective to properties of some types of synthetic chemical pesticides or in the production of bio-pesticides directly (Kasprowicz *et al.*, 2010).

Silver Nanoparticles have shown promise against *Pseudomonas syringae*. The use of nano-sized silver particles as antimicrobial agents has become more common as technological advances make their production more economical. One of the potential applications in which silver can be utilized is in management of plant diseases. Since silver displays multiple modes of inhibitory action

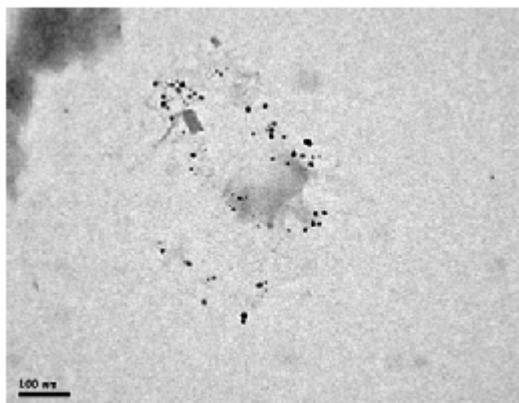


Fig. 6. Images of biosynthesized silvernanoparticles by Transmission Electron Microscopy (TEM)

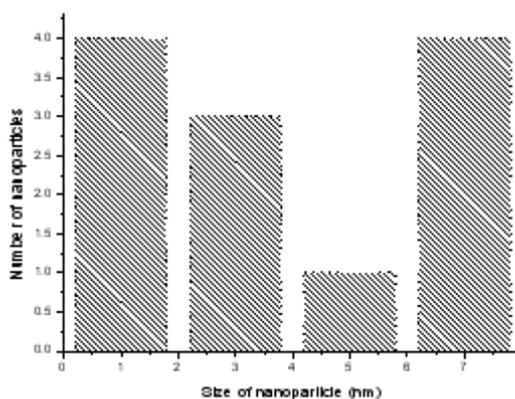


Fig. 7. Histogram for different sizes of biosynthesized silver nanoparticles from TEM images



Fig. 8. Antimicrobial activity of AgNPs (5 μ l) against *Pseudomonas syringae*

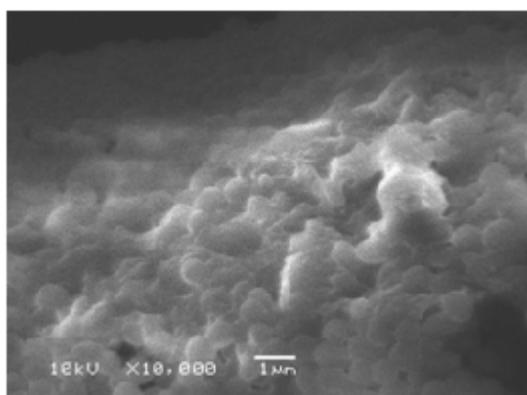
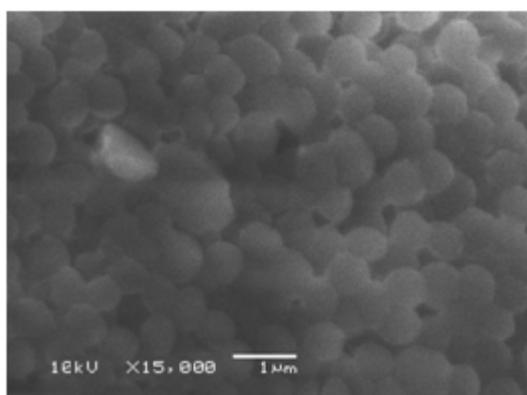


Fig. 9. Effect of AgNPs on growth of *Pseudomonas syringae* cell under scanning electronic microscope (SEM). Untreated cells (left) and treated cells (right)

to microorganisms, it may be used for controlling various plant pathogens in a relatively safer way compared to synthetic fungicides (Kasprowicz *et al.*, 2010). Until now, limited research provided some evidence of the applicability of silver for controlling plant diseases (Kasprowicz *et al.*, 2010). This is considered a successful development of alternative pesticides synthesis.

CONCLUSION

In this study, it has been demonstrated that *S. bikiniensis* is capable of producing silver nanoparticles extracellularly and these nanoparticles are quite stable in solution. The characterization of Ag^+ ions exposed to this filtrate of *S. bikiniensis* by SDS techniques confirmed the reduction of silver ions to silver nanoparticles. The TEM image suggests that the particles are monodispersed and spherical silver nanoparticles (AgNPs) in the size range of 1-7 nm. SEM suggests that aggregated particles due to the capping agent. It is concluded also that the biosynthesized nanoparticles by *S. bikiniensis* have a potential and biocidalefficacy to inhibit and stop the growth of the plant pathogen *Pseudomonas syringae*. This new findings of silver nanoparticles will be considered to be important components of integrated pest management (IPM), and should be received much practical attention as substitutes to synthetic pesticides for plant protection.

ACKNOWLEDGMENTS

The author extended their appreciation to the Deanship of Scientific Research at King Saud University for their funding the work through the research group project No. RGP-VPP-010.

REFERENCES

1. Antony, J.J., Sivalingam, P., Siva, D., Kamalakkannan, S., Anbarasu, K., Sukirtha, R., Krishnan, M, Achiraman, S., *Colloids Surf.*, 2011; **B88**: 134–140.
2. Anzai, Y., Kim, H., Park, J.Y. Wakabayashi, H; Oyaizu, H. Phylogenetic affiliation of the pseudomonads based on 16S rRNA sequence. *International journal of systematic and evolutionary microbiology*, 2000; **504**: 1563–89.

3. Bai, H.J., Yang, B.S., Chai, G.J., Yang, G.E., Jia, W.L., Yi Green, Z.B. synthesis of silver nanoparticles using *Rhodobacter Sphaeroides*, *World J Microbiol Biotechnol.*, 2011; doi:10.1007/s11274-011-0747-x.
4. Bhattacharya, D., Gupta, R.K., Nanotechnology and Potential of Microorganisms, *Critical Reviews in Biotechnol*, 2005; **25**: 199.
5. Bragg P.D., Rainnie, D.J., Can, J. The effect of silver ions on the respiratory chain of *Escherichia coli*, *Microbiol.*, 1974; **206**: 883-9.
6. Chater, K.F., Genetic differentiation of *streptomyces*, *Annu. Rev. Microbiol*, 1993; **47**: 685-713.
7. Cody, Y.S., Gross, D.C. Characterization of Pyoverdinpss, the Fluorescent Siderophore Produced by *Pseudomonas syringae*pv. *syringae*. *Applied and environmental microbiology*, 1987; **535**: 928-34.
8. Dura, N., Marcato, P., Alves, O., De Souza, G., Esposito, E., Mechanistic aspects of biosynthesis of silver nanoparticles by several *Fusarium oxysporum* strains, *J. Nanobiotechnol*, 2005; **3**: 8.
9. Elechiguerra, J., Burt, J., Morones, J., Camacho-Bragado, A., Gao, X., Lara, H., Yacaman, M. Interaction of silver nanoparticles with HIV-1. *J Nanobiotechnol.*, 2005; **3**: 6.
10. Fei, Z., Joung, J.G., Tang, X., Zheng, Y., Huang, M., Lee, J.M., McQuinn, R., Tieman, D.M., Alba, R., Klee, H.J., & Giovannoni, J.J. Tomato Functional Genomics Database: a comprehensive resource and analysis package for tomato functional genomics. *Nucleic Acids Research Database*, 2011; D1156-D1163.
11. Felsenstein, J., Confidence limits on phylogenies: an approach using the bootstrap, *Evolution*, 1985; **39**: 783-791.
12. Feng Q.L., Wu, J., Chen, G.Q., Cui, F.Z., Kim, T.N., Kim, J.O., A mechanistic study of the antibacterial effect of silver ions on *Escherichia coli* and *Staphylococcus aureus*, *Biomed Mater Res*. 2000; **15**: 524: 662-8.
13. Gole, A., Dash, C., Ramakrishnan, V., Sainkar, S.R., Mandale, A.B., Rao, Sastry, M.M, Pepsingold colloid conjugates, Preparation, characterization, and enzymatic activity, *Langmuir*, 2001; **17**: 1674.
14. Hayakawa, M., Ohara, Y., Humic acid-vitamin agar, a new medium for the selective isolation of soil actinomycetes, *J. Ferment. Technol*, 1987; **65**: 501-509.
15. Hayat, M.A. , Principles and techniques of electron microscopy, *London: Edward Arlond Lt.*, 1981; **1**: p 522.
16. Jain, N., Bhargava, A., Majumdar, S., Tarafdarb, J.C., Panwar, J. Extracellular biosynthesis and characterization of silver nanoparticles using *Aspergillus flavus* NJP08 A mechanism perspective, *Nanoscale*, 2011; **3**: 635.
17. Jukes, T.H., Cantor, C.R. Evolution of protein molecules, in: Mammalian Protein metabolism III, *Academic Press, London*, 1969; pp. 21–132.
18. Kaluzna, M., Pulawska J., Sobiczewski P. The use of PCR melting profile for typing of *Pseudomonas syringae* isolates from stone fruit trees. *European Journal of Plant Pathology*, 2010; **126**: 437-443.
19. Kasprowicz, J. M., Kozio³. M., and Gorczyca, A.. The effect of silver nanoparticles on phytopathogenic spores of *Fusarium culmorum*. *Canadian Journal of Microbiology*, 2010; **3**: 247-253.
20. Klaus, T.J., Jeorger, R., Olsson, E., Granqvist, C., Bacteria as workers in the living factory: metal accumulating bacteria and their potential for material science, *Trends Biotechnol*, 2001; **19**: 15–20.
21. Kumar, S., Abyaneh, M., Gosavi, S., Kulkarni, S., Pasricha, R., Ahmad, A., Khan, M., Nitrate reductase-mediated synthesis of silver nanoparticles from AgNO₃, *Biotechnol. Lett.*, 2007; **29**: 439–445.
22. Kumar, V., Yadav S.K. Plant-mediated synthesis of silver and gold nanoparticles and their applications. *J. Chem. Technol. Biotechnol.*, 2009; **84**: 151.
23. Magudapathy, P., Gangopadhyay, P., Panigrahi, B.K., Nair K.G.M., Dhara, S., Electrical transport studies of Ag nanoclusters embedded in glass matrix, *Phys.*, 2001; B. 299, 142.
24. McDonnell, G., Russell, A.D. Review Antiseptics and disinfectants: activity, action, and resistance, *Clin Microbiol Rev.*, 1999; **121**: 147-179.
25. Mince, T.J., Jensen, P.R., Kauffman, C.A., Fenical, W., *Appl. Environ. Microbiol.*, 2002; **68**: 5005-5011.
26. Mohanpuria, P., Rana N.K., Yadav, S.K., Biosynthesis of nanoparticules, technological concepts and future applications, *J. of Nanoparticle Res.*, 2008; **10**: 507.
27. Mukherjee, P., Roy, M., Mandal, B.P., Dey, G.K., Mukherjee, P.K., Ghatak, J., Tyagi, A.K., Kale, S.P., *Nanotechnology*, 2008; **19**: 75103.
28. Mulvaney, P., Surface plasmon spectroscopy of nanosized metal particles, *Langmuir*, 1996; **12**: 788-800.
29. Niederhauser, J.S. International cooperation in potato research and development. *Annual Review*

- of *Phytopathology*, 1993; **311**: 1-25.
30. Pisano, A.M., Sommer, J.M., Lopez, M.M., Application of pretreatment for the isolation of bioactive actinomycetes from marine sediments, *Appl. Microbiol. Biotechnol.*, 1986; **25**: 285-288.
 31. Sadhasivam, S., Shanmugam, P., Yun, K.S. Biosynthesis of silver nanoparticles by *Streptomyces hygroscopicus* and antimicrobial activity against medically important pathogenic microorganisms, *Colloids Surf*, 2010; **B 81**:358–362.
 32. Saifuddin, N., Wong, C., Yasumira, A., Rapid biosynthesis of silver nanoparticles using culture supernatant of bacteria with microwave irradiation, *EJ Chem.*, 2009; **61**: 61–70.
 33. Saitou, N., Nei, M., The neighbor-joining method: a new method for reconstructing phylogenetic trees, *Mol. Biol. Evol.*, 1987; **4**: 406–425.
 34. Scholz-Schroeder, Brenda, K.; Soule, D.; Gross, Dennis C. The *sypA*, *sypB*, and *sypC* Synthetase Genes Encode Twenty-Two Modules Involved in the Nonribosomal Peptide Synthesis of Syringopeptin by *Pseudomonas syringae* pv. *syringae* B301D". *Molecular Plant-Microbe Interactions*, 2003; **16**(4): 271–280.
 35. Shirling, E.B., Gottlieb, D., Methods for characterization of *Streptomyces* species, *Int J. Syst Bacteriol.*, 1966; **16**: 313–340.
 36. Sivalingama, P., Antony, J., Sivab, D., Achiramanb, S., Anbarasua, K., Mangrove *Streptomyces* sp. BDUKAS10 as nanofactory for fabrication of bactericidal silver nanoparticles, *Colloids and Surfaces B: Biointerfaces*, 2012; **98**: 12– 17.
 37. Smoker, J.A., Barnum, S.R. Rapid small-scale DNA isolation from filamentous cyanobacteria, *FEMS microbiol. Letters*, 1988; **561**: 119-122.
 38. Sondi, I., Salopek-Sondi, B., Silver nanoparticles as antimicrobial agent: a case study on *Escherichia coli* as a model for Gram-negative bacteria, *J. Colloid Interface Sci.*, 2004; **2751**: 177-182.
 39. Stoimenov, P.K., Klinger, R.L., Marchin, G.L., and Klabunde, K.J. Metal oxide nanoparticles as bactericidal agents. *Langmuir*, 2002; **18**: 6679-6686.
 40. Thompson, J.D., Gibson T.J., Plewniak, F., Jeanmougin, F., Higgins D.G. The CLUSTAL_X windows interface: flexible strategies for multiple sequence alignment aided by quality analysis tools, *Nucleic Acids Res.*, 1997; **25**: 4876–4882.
 41. Yamanaka, M., Hara, K., Kudo, J., Bactericidal actions of a silver ion solution on *Escherichia coli*, studied by energy-filtering transmission electron microscopy and proteomic analysis, *Appl Environ Microbiol.*, 2005; **7111**: 7589-93.